

Revista Portuguesa de Estomatologia, Medicina Dentária e Cirurgia Maxilofacial

www.elsevier.pt/spemd



Original research

Effects of salivary acetylcholinesterase on the cytotoxicity of acrylic reline resins



Miguel Constantino Mendes De Oliveira^{a,*}, Luis Pires Lopes^a, Joana Miranda^b,
Matilde Castro^b, Ana Francisca Bettencourt^b, Cristina Bettencourt Neves^a

^a Biomedical and Oral Sciences Research Unit (UICOB), Faculty of Dental Medicine, University of Lisbon, Lisbon, Portugal

^b Research Institute for Medicines and Pharmaceutical Sciences (iMed.UL), Faculty of Pharmacy, University of Lisbon, Lisbon, Portugal

ARTICLE INFO

Article history:

Received 9 August 2013

Accepted 1 December 2013

Available online 17 January 2014

Keywords:

Acrylic resins

Acetylcholinesterase

Fibroblasts

Inhibitory concentration 50

ABSTRACT

Aim: To evaluate the effect of acetylcholinesterase on the cytotoxicity of three autopolymerizing acrylic reline resins through the effect of the materials' eluates, liquids and respective pure compounds on the cellular viability of primary dermal fibroblasts cultures.

Methods: Disk shaped specimens of two direct Acrylic Reline Resins (ARR), Kooliner and Ufi Gel Hard, and one indirect ARR, Probosc Cold, were studied. Cytotoxicity was studied through spectrophotometric determination of tetrazolium reduction (MTT assay) and lactate dehydrogenase activity (LDH assay). Moreover, at least 7 concentrations of each liquid and compound were prepared to determine the IC50 parameter. All data were evaluated using Kruskal–Wallis or Mann–Whitney test, after verification with Kolmogorov–Smirnov test.

Results: The fibroblasts exposed to the direct ARR eluates resulted in inhibition of the mitochondrial activity. Probosc Cold eluates did not diminish cellular viability. LDH remained unaltered when fibroblasts were exposed to the eluates. Acetylcholinesterase groups of direct reline resins showed to be less cytotoxic when compared with control groups without changing their cytotoxic potential. The non-cytotoxic effect of Probosc Cold did not change. The cytotoxicity of the pure compounds increased in the following order: Methacrylic Acid (MA), Isobutyl Methacrylate (IBMA) and Hexanediol Dimethacrylate (HDMA). Methyl Methacrylate (MMA) showed no cytotoxicity at the concentrations used. The direct reline resins liquids and respective pure compounds exhibited similar behavior.

Conclusions: Acetylcholinesterase did not change the cytotoxic potential of the reline resins studied. HDMA and IBMA revealed higher levels of cytotoxicity than MA, and their behavior was similar to the respective liquids.

© 2013 Sociedade Portuguesa de Estomatologia e Medicina Dentária. Published by Elsevier España, S.L. All rights reserved.

* Corresponding author.

E-mail address: Oliveira.miguel90@gmail.com (M.C. Mendes De Oliveira).

1646-2890/\$ – see front matter © 2013 Sociedade Portuguesa de Estomatologia e Medicina Dentária. Published by Elsevier España, S.L. All rights reserved.

<http://dx.doi.org/10.1016/j.rpemd.2013.12.134>

Efeito da enzima salivar acetilcolinesterase na citotoxicidade de resinas acrílicas de rebasamento

R E S U M O

Palavras chave:

Resinas acrílicas

Acetilcolinesterase

Fibroblastos

Concentração inibitória 50

Objetivos: Avaliar o efeito da acetilcolinesterase na citotoxicidade de três resinas acrílicas de rebasamento autopolimerizáveis (RRA), através do efeito dos extractos totais dos materiais, dos líquidos e dos respetivos monómeros puros na viabilidade de culturas primárias de fibroblastos.

Métodos: Foram avaliadas duas RRA diretas, Kooliner e Ufi Gel Hard, e uma resina de rebasamento indirecto, Probace Cold. A citotoxicidade foi determinada através de ensaios espectrofotométricos da redução do brometo de tetrazólio (MTT) e da atividade da enzima lactato desidrogenase (LDH), em culturas primárias de fibroblastos. Adicionalmente, foram preparadas, pelo menos, 7 concentrações de cada monómero e líquido, para determinar o parâmetro IC50. Os dados foram analisados por meio do teste Kruskal-Wallis ou Mann-Whitney, após verificação com teste de Kolmogorov-Smirnov.

Resultados: A exposição dos fibroblastos aos extratos das RRA diretas resultou na inibição da atividade mitocondrial, enquanto o Probace Cold não provocou diminuição da viabilidade celular. A atividade da LDH não sofreu alterações quando exposta aos extratos. Os grupos com acetilcolinesterase das RRA directas revelaram-se menos tóxicos, quando comparados com os grupos controlo, sem alterar o seu potencial citotóxico. A citotoxicidade dos monómeros puros aumentou na seguinte ordem: ácido metacrílico (MA), isobutilmetacrilato (IBMA) e hexanodiol dimetacrilato (HDMA). Os líquidos das resinas de rebasamento directo demonstraram uma curva de citotoxicidade semelhante aos respetivos monómeros.

Conclusões: A enzima acetilcolinesterase não alterou o potencial citotóxico dos materiais estudados. O HDMA e IBMA demonstraram maiores níveis de citotoxicidade que o ácido Metacrílico, e o seu comportamento foi semelhante ao líquido das respetivas resinas.

© 2013 Sociedade Portuguesa de Estomatologia e Medicina Dentária. Publicado por Elsevier España, S.L. Todos os direitos reservados.

Introduction

The use of autopolymerizing acrylic resin resins (ARR) has recently gained popularity in dentures readjustment to the continuous reabsorbed underlying tissues, providing better retention and stability for complete removable prostheses.^{1,2}

However, these materials have been associated with *in vitro* toxicity and also, *in vivo* manifestations such as chemical irritation, allergic reactions,^{1,3} erythema, erosion of oral mucosa and burning mouth sensation.⁴ These adverse reactions caused by denture base polymers have been attributed to substances leached from these materials, especially unreacted residual monomers (RM), that remained in the resin net after polymerization.⁵⁻⁷

Given the generally reliable manufacturers intended lifetime of polymeric devices,⁸ several studies have shown that polymers may be subject to numerous biodegradation processes in the oral cavity,⁹ due to the important role that esterases plays in the enzymatic activity. Acetylcholinesterase (AChE) catalytic activity has recently been shown to be detectable in saliva where its catalytic activity is stable.¹⁰ However, other study findings indicated that the intra-individual coefficient of variance of saliva AChE was 35%,¹¹ showing that levels of this enzyme are highly variable.

Although well demonstrated in composite resins,¹²⁻¹⁴ the role of esterases on the biodegradation of ARR needs further investigation.

The main purpose of the present study was to investigate the influence of acetylcholinesterase on the level of cytotoxicity of three widely used autopolymerizing ARR. In addition, the purpose was to assess the level of cytotoxicity of three specific pure compounds, that are known to be present in the eluates, and the cytotoxicity of the resin liquids through the determination of the half maximal inhibitory concentration (IC50).

Materials and methods

This study enrolled two direct ARR, Kooliner (GC America Inc., Alsio, IL, USA), Ufi Gel Hard (Voco GmbH, Cuxhaven, Germany), and one indirect ARR, Probace Cold (Ivoclar Vivadent AG, Schaan, Liechtenstein), in powder liquid form (Table 1). Disk shaped specimens were prepared from three separate mixtures in stainless steel molds, with an average diameter of 50 ± 0.1 mm and an average thickness of 2 ± 0.01 mm, according to ISO recommendation for biological evaluation of biomaterials.^{15,16}

Direct ARR were set at $37 \pm 2^\circ\text{C}$ for the recommended polymerization time (Table 1) in order to simulate the intra-oral polymerization of the material. Polymerization of indirect ARR was carried out in a Ivomat pressure device (Ivoclar Vivadent, Lichtenstein) for the recommended time, temperature and pressure (Table 1).

After UV sterilization,¹⁷⁻¹⁹ specimens of each material ($n=6$) were randomly divided into two groups: experimental,

Table 1 – Materials under evaluation in the study.

Product	Manufacturer	Batch number	P/L ratio	Composition	Curing cycle
Kooliner (K)	GC America Inc., Alsip, IL, USA	1007201 (P) 1008101 (L)	1.4/1	P: PEMA L: IBMA	10 min
Ufi Gel Hard (U)	VocoGmbH, Cuxhaven, Germany	1133100 (P) 1134070 (L)	1.77/1	P: PEMA L: HDMA	7 min
Probase Cold (P)	Ivoclar Vivadent AG, Liechtenstein	L49853 (P) L43809 (L)	1.5/1	P: PMMA L: MMA	15 min40°, 2–4 bar

immersed in 5 mL of serum-free DMEM with 5 U/mL of AChE and control, immersed only in 5 mL of serum-free DMEM. The volume of the medium was selected in order to cover the entire surface of each specimen.¹⁵

Specimens were incubated for 72 h at 37 °C under constant agitation to allow the soluble components to leach into the medium.²⁰ Every 24 h, 5 U/mL of AChE (Sigma-Aldrich Co., St. Louis, MO, USA) was added to experimental specimens in order to maintain the enzyme activity and DMEM was added to control specimens. The medium without specimens was also incubated as above to serve as the negative control and medium with enzyme without specimens to serve as the enzyme control.

All specimens' eluates were then diluted in fresh supplemented DMEM as follows: no dilution (100%), 3:4 dilution (75%) and 1:2 dilution (50%), to check the dose-dependent response of the cultured cells, following ISO instructions to measure accuracy.²¹

The cytotoxic evaluation of the eluates was carried out through the reduction of 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl-2H-tetrazolium bromide by mitochondrial dehydrogenases (MTT) and by the release of a soluble cytosolic enzyme, lactate dehydrogenase (LDH), into the cell culture medium as the marker for membrane damage.^{22,23}

Cell culture procedure was adapted from a method previously described.²⁴ Human Adult Dermal Fibroblast Cells (Zen-Bio Inc., Chapel Hill, USA) were routinely cultured in DMEM (Sigma-Aldrich Co., St. Louis, MO, USA) with 3.15 g/L of D-glucose (Sigma-Aldrich Co., St. Louis, MO, USA), 11.4% FBS (Sigma-Aldrich Co., St. Louis, MO, USA), and 1% penicillin-streptomycin solution (Sigma-Aldrich Co., St. Louis, MO, USA). The cells were grown under an atmosphere containing 5% of CO₂.

Cells were then inoculated into 96-well culture plates at a density of 3.2×10^3 cells/well and incubated at 37 °C under a 5% CO₂ atmosphere. After 24 h, the supernatant was removed and cells were then treated for a further 24 h period with 200 µL per well of serial dilutions of the eluates ($n=8$) per combination. Previously explained enzyme and negative control as well as positive control (incubation with DMSO 20%) were used in each assay.²⁵

After the 24 h incubation, the medium was carefully removed from each plate and pipetted to a new vial, to be used later in the LDH assay (Sigma-Aldrich Co., St. Louis, MO, USA).

The remaining cells were incubated with 200 µL of MTT solution (0.5 mg/mL, Sigma-Aldrich Co., St. Louis, MO, USA) for a further period of 2.5 h at 37 °C. After this period, the MTT solution was discharged and a soluble solvent, DMSO,

was added to each well to dissolve the formazan crystals. Absorbance was read at a wavelength of 595 nm (Spectrostar Omega, BMG LABTECH, Ortenberg, Germany).

The medium previously removed from the 96 well plates was then centrifuged at $10,000 \times g$ for 10 min. The supernatant (25 µL) was moved to a new 96-well plate along with a mixture of PBS and reconstituted substrate mix already prepared from the LDH Kit (tox-7, Sigma-Aldrich, St. Louis, USA). Plates were then kept for 24 min in the dark at room temperature. Absorbance was recorded both at 490 and 690 nm on a spectrophotometer (Spectrostar Omega, BMG LABTECH, Germany).

Three independent experiments were performed with eight replicate cultures used for each test solution and controls in each independent experiment. The mean and standard error of the mean absorbance for each test solution were calculated from the triplicate samples. Results of the colorimetric assays were expressed as percentage of viable cells yielded by the test solutions compared to negative controls.

The Kolmogorov-Smirnov test was used to assess the normality of cell viability variable. Mann-Whitney tests were used to compare cell viability between control and AChE groups. To compare materials, test compounds and dilutions, Kruskal-Wallis was used, followed by post testing Tukey multiple comparison. p -Values ≤ 0.05 were considered significant.

In order to get clear insight on the role of monomers on the cytotoxicity of these materials, the cellular viability was also assessed after exposure to Isobutyl Methacrylate (IBMA), Hexanediol Dimethacrylate (HDMA), Methyl Methacrylate (MMA) and the common hydrolysis by-product Methacrylic Acid (MA), taking into account the IC₅₀ (half maximal inhibitory concentration of a substance). The IC₅₀ of the ARR liquids was also studied. All the above mentioned compounds were purchased from Sigma-Aldrich Co. (St. Louis, MO, USA) with the exception for MMA which was obtained from Merck, KgaA (Schuchardt, Germany).

At least seven concentrations of each liquid and compound were diluted in DMEM supplemented with ethanol at a final concentration of $\leq 0.3\%$, in order to obtain the IC₅₀, through the MTT assay.^{26,27}

IC₅₀ was determined using a non-linear regression of dose-response – inhibition type [log(inhibitor) vs. normalized response – variable slope].

Results

Fig. 1 shows no cytotoxicity for Probase Cold control specimens, ~90% decrease in cell viability for Kooliner control

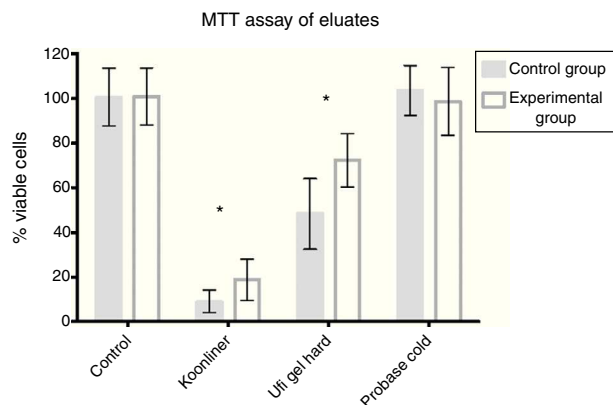


Fig. 1 – Effect of acetylcholinesterase on the cytotoxicity of 3 reline resins expressed as percentage of viable fibroblast present after exposure compared with the negative control group set as 100%; * means significant differences between experimental and control groups.

specimens and ~51% decrease in cell viability for UfiGel Hard control specimens. Differences between the three materials were statistically significant ($p < 0.001$).

Kooliner specimens submitted to treatment with AChE showed a slight increase of cell viability ($18.8 \pm 9.2\%$) compared with the control specimens ($9.0 \pm 4.9\%$, $p < 0.001$). For Ufi Gel Hard specimens, the cell viability of the experimental group submitted to AChE ($72.5 \pm 12\%$) also showed an increase compared with the specimens incubated only in the culture medium ($48.3 \pm 15.8\%$, $p < 0.001$) as recorded in Fig. 1. AChE did not change the non-cytotoxic effect of Probace Cold specimens.

The data indicated a dose-dependent effect on cytotoxicity for the different dilutions of Kooliner and Ufi Gel Hard eluates, as shown in Fig. 2.

At the LDH assay, neither control nor AChE groups demonstrated differences when compared with negative control groups (Fig. 3).

Approximately 50% of the cellular viability of the compound groups were affected when 0.2715 mmol/L of HDMA, 3.521 mmol/L of IBMA, 31.88 mmol/L of MA were used. MMA

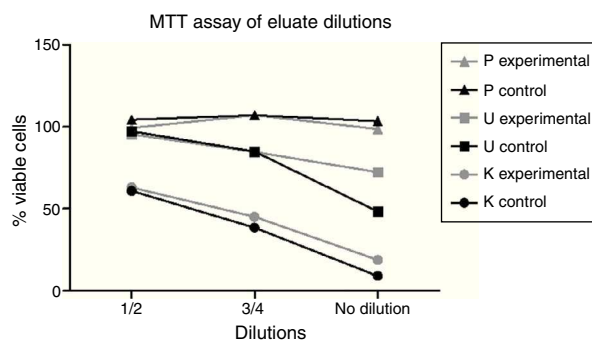


Fig. 2 – Cytotoxicity of Kooliner (K), Ufi Gel Hard (U) and Probace Cold (P) dilutions expressed as percentage of viable fibroblasts present after exposure compared with the negative control group set as 100%.

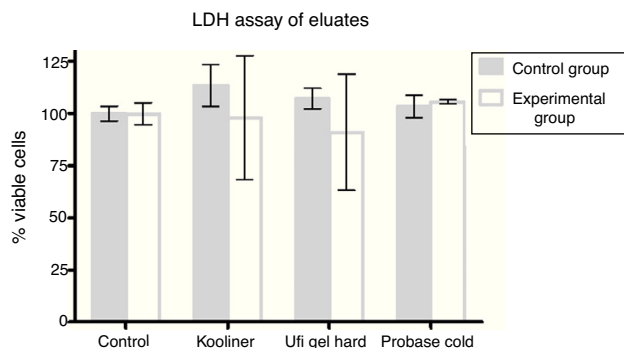


Fig. 3 – Effect of acetylcholinesterase on the cytotoxicity of 3 reline resins expressed as percentage of viable fibroblast present after exposure compared with the negative control group set as 100%.

showed no cytotoxicity at the concentrations used, and hence it was not possible to determine IC₅₀ (Figs. 4–7).

Figs. 5–7 exhibit point-to-point curves of resins liquids and respective monomers. The IC₅₀ of the ARR liquids is obtained with, respectively, 0.2587 mmol/L of Ufi Gel Hard, 6.496 mmol/L of Kooliner and 7.124 mmol/L of Probace Cold.

The curve shape of the monomers in Figs. 5 and 6, matched with the resins liquids, exhibiting similar behavior.

Discussion

The exposure of fibroblasts to direct ARR eluates resulted in a significant suppression of the mitochondrial activity. This result is in accordance with a previous study that also used human fibroblasts.²⁴ Nevertheless, in the other study,¹⁹ direct ARR eluates did not show any toxic effects on the L929 mouse lung fibroblasts cell line. These results could be explained by the distinct type of cells used in the studies. Several authors reported that primary cells have greater sensitivity than transformed lines when testing various biomaterials used in dentistry.^{3,28} Primary cultures correlate to an *in vivo* response more accurately, so they can be considered to be

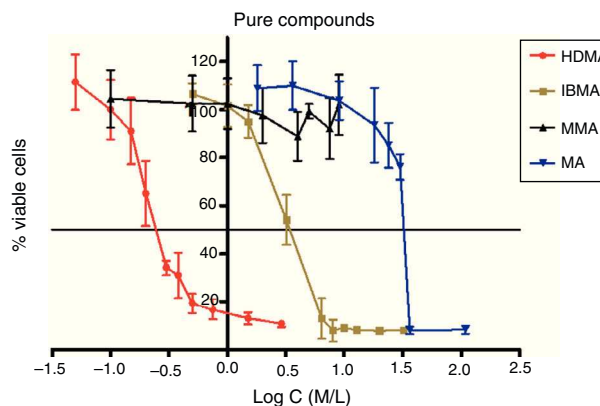


Fig. 4 – Cellular viability as determined by MTT assay. Comparison of percentage of cellular viability of cells treated with increasing concentrations of pure compounds for 24 h. Results are expressed as the mean $\pm$ SD.

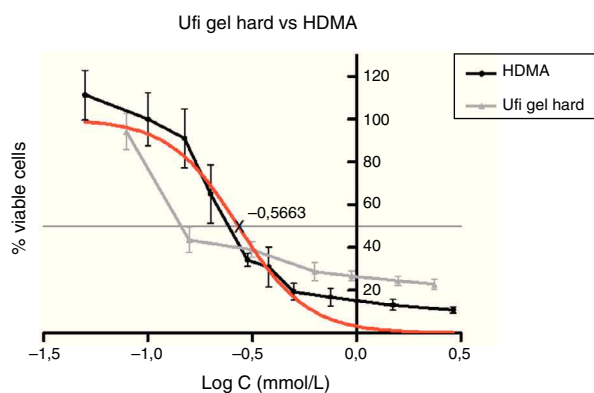


Fig. 5 – Cellular viability as determined by MTT assay. Comparison of percentage of cellular viability of cells treated with increasing concentrations of HDMA and Ufi Gel Hard liquid for 24 h. Results are expressed as the mean $\pm$ SD IC50 determination.

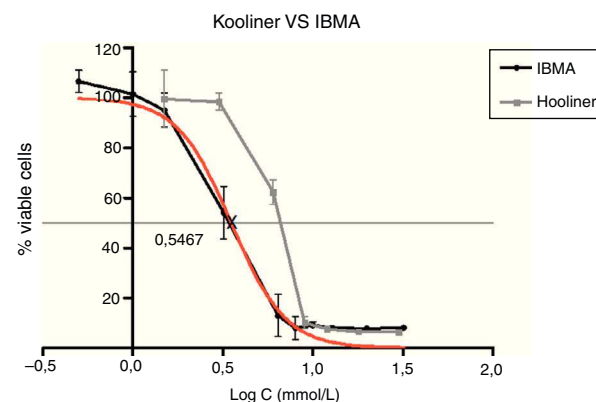


Fig. 6 – Cellular viability as determined by MTT assay. Comparison of percentage of cellular viability of cells treated with increasing concentrations of IBMA and Kooliner liquid for 24 h. Results are expressed as the mean $\pm$ SD IC50 determination.

more appropriate for testing toxicity of materials for human use.²⁴

Even though several previous studies have shown that indirect autopolymerized eluates were cytotoxic to fibroblasts,^{29-31,17} the present study did not find cytotoxicity on eluates of Probase Cold. This can be explained by the recommended pressure and temperature treatment during the polymerization, in which the indirect ARR used in our study was exposed, in opposition to the polymerization at room temperature used in the mentioned studies.^{3,32}

Kooliner showed a higher cytotoxic effect than Ufi Gel Hard in control specimens. The fact that Kooliner showed a higher percentage of RM content than Ufi Gel Hard^{24,33,34} could explain this difference. A previous study³⁵ found that the more monomer added to the mixture the greater the amount of RM and therefore the higher the potential for cytotoxicity. The greater RM available in the Kooliner can be explained by the lower powder/liquid ratio. Previous

studies have already shown that post-polymerization treatment whether with immersion in hot water or ethanol aqueous solutions at 55 °C can reduce this RM content; the latter being more effective in decreasing the cytotoxicity of both materials.³⁶

In this study, Ufi Gel Hard eluates suppressed around 51% cell viability. In spite of the severe cytotoxicity potential of HDMA, defended by some authors,^{24,26} the low levels of RM content of this resin promoted only moderately cytotoxic effects over the fibroblast cells.

In contrast, the highly toxic effect of Kooliner eluates (~10% of viable cells) cannot be explained solely by a higher percentage of residual IBMA content of specimens. This may also be due to differences in quantity and quality of other potentially toxic compounds^{32,37,38} that may be released from the resins as cross linking agents, initiator, plasticizers like ethylene glycol dimethacrylate (EGDMA) or tetramethylene dimethacrylate (TMDMA),³⁹ pigments, degradation

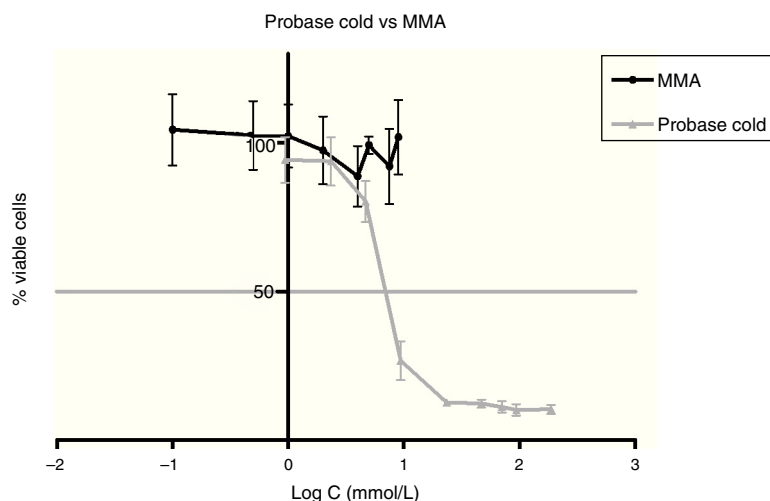


Fig. 7 – Cellular viability as determined by MTT assay. Comparison of percentage of cellular viability of cells treated with increasing concentrations of MMA and Probase Cold liquid for 24 h. Results are expressed as the mean $\pm$ SD IC50 determination.

by-products like MA and newly formed formaldehyde.⁴⁰ In addition, potential synergetic effects of the leachable chemicals should also be considered.²⁴

The experimental specimens from direct ARR revealed an increase of cell viability when compared to respective control groups. The increase of cell viability of experimental Kooliner specimens can be explained by the hydrolysis of IBMA promoted by the enzymatic reaction. MA was found to be a product of this reaction, but the lower cytotoxic potential of MA comparing to IBMA demonstrated by this study and before by several groups^{24,26} can explain the reduction of the cytotoxicity. In addition, MA proved to be a very unstable compound in aqueous solutions.⁴¹

In contrast, the slender increase of cell viability of experimental Ufi Gel Hard specimens could not be related to the enzymatic reaction since HDMA was found to be resistant to AChE. However, levels of MA obtained in other studies reveal that AChE promoted production of MA by hydrolysis of monomers others than HDMA that can be present in Ufi Gel Hard specimens.²⁴

Within the present study, results of the dilutions of eluates showed an increase of cell viability in a dose dependent manner.

Among the tested materials, the Ufi Gel Hard liquid and its monomer, 1,6-HDMA, showed the greatest toxic effects, whereas MMA had the smallest effect. Both Kooliner liquid and IBMA showed moderate cytotoxicity.

The presence of IBMA and 1,6-HDMA explains the cytotoxic effects observed for Kooliner liquid and Ufi Gel Hard liquid, respectively. However, even in higher concentrations, MMA showed no cytotoxic effect on fibroblasts. MMA alone cannot completely explain the effects of Probase Cold liquid on the viability of cells. The effects of Probase Cold liquid in the cellular viability can be explained by the hydrolysis of the monomer MMA in MA, or by its composition which besides MMA contains a plasticizer, tetramethylene dimethacrylate. The effect of this compound on the fibroblasts viability is still unknown.

Conclusions

Within the limitations of this study, the main conclusions are:

- Incubation with acetylcholinesterase did not change the non-cytotoxic effect of Probase Cold.
- Incubation with AChE caused a slight increase in cell viability of both direct ARR (Kooliner and Ufi Gel Hard), without changing their cytotoxic potential.
- The cytotoxicity of the pure compounds increased in order: MA < IBMA < HDMA. MMA showed no cytotoxicity at the concentrations used.
- The direct ARR liquids and respective pure compounds exhibited similar behaviors.

Ethical disclosures

Protection of human and animal subjects. The authors declare that no experiments were performed on humans or animals for this investigation.

Confidentiality of data. The authors declare that no patient data appear in this article.

Right to privacy and informed consent. The authors declare that no patient data appear in this article.

Conflicts of interest

The authors have no conflicts of interest to declare.

Acknowledgments

The authors would like to thank Voco GmbH (Cuxhaven, Germany) for the donation of the Ufi Gel Hard material evaluated in this study and Fundação para a Ciência e Tecnologia (Portugal) (PEst-OE/SAU/UI4062/2011; PEst-OE/SAU/UI4013/2011; Ciência 2008 for J. P. M. and EXCL/CTMNAN/0166/2012) for providing financial support to this project.

REFERENCES

1. Bohnenkamp DM. Traumatic stomatitis following an intraoral denture relining: a clinical report. *J Prosthet Dent.* 1996;76:113-4.
2. Aydin AK, Terzioğlu H, Akinay AE, Ulubayram K, Hasirci N. Bond strength and failure analysis of lining materials to denture resin. *Dent Mater.* 1999;15:211-8.
3. Huang FM, Tai KW, Hu CC, Chang YC. Cytotoxic effects of denture base materials on a permanent human oral epithelial cell line and on primary human oral fibroblasts in vitro. *Int J Prosthodont.* 2001;14:439-43.
4. Jorge JH, Giampaolo ET, Machado AL, Vergani CE. Cytotoxicity of denture base acrylic resins: a literature review. *J Prosthet Dent.* 2003;90:190-3.
5. Gonçalves TS, Morganti MA, Campos LC, Rizzato SM, Menezes LM. Allergy to autopolymerized acrylic resin in an orthodontic patient. *Am J Orthod Dentofacial Orthop.* 2006;129:431-5.
6. Celebi N, Yuzugullu B, Canay S, Yucel U. Effect of polymerization methods on the residual monomer level of acrylic resin denture base polymers. *Polym Adv Technol.* 2008;19:201-6.
7. Golbidi F, Asghari G. The level of residual monomer in acrylic denture base materials. *Res J Biol Sci.* 2009;4:244-9.
8. Coury A. Degradation of materials in the biological environment: chemical and biochemical degradation of polymers. In: Ratner B, Hoffman A, Schoen FJ, Lemons JE, editors. *Biomaterials science – an introduction to materials in medicine.* 2nd ed. London, UK: Elsevier Academic Press; 2004.
9. Bettencourt AF, Neves CB, Almeida MA, Pinheiro LM, Oliveira SA, Lopes LP, et al. Biodegradation of acrylic based resins: a review. *Dent Mater.* 2010;26:e171-80.
10. Ng V, Koh D, Wee A, Chia SE. Salivary acetylcholinesterase as a biomarker for organophosphate exposure. *Occup Med.* 2009;59:120-2.
11. Claus Henn B, McMaster S, Padilla S. Measuring cholinesterase activity in human saliva. *J Toxicol Environ Health A.* 2006;69:1805-18.
12. Munksgaard EC, Freund M. Enzymatic hydrolysis of (di)methacrylates and their polymers. *Scand J Dent Res.* 1990;98:261-7.
13. Larsen IB, Munksgaard EC. Effect of human saliva on surface degradation of composite resins. *Scand J Dent Res.* 1991;99:254-61.

14. Hagio M, Kawaguchi M, Motokawa W, Miyazaki K. Degradation of methacrylate monomers in human saliva. *Dent Mater J*. 2006;25:241-6.
15. International Standard ISO Specification 10993-12. Biological evaluation of medical devices. Part 12: Sample preparation and reference material. 3rd ed. Geneva, Switzerland: International Organization for Standardization; 2007.
16. International Standard ISO Specification 20795-1. Dentistry-base polymers. Part 1: Denture base polymers. 1st ed. Geneva, Switzerland: International Organization for Standardization; 2008.
17. Sheridan PJ, Koka S, Ewoldsen NO, Lefebvre CA, Lavin MT. Cytotoxicity of denture base resins. *Int J Prosthodont*. 1997;10:73-7.
18. Jorge JH, Giampaolo ET, Vergani CE, Machado AL, Pavarina AC, Carlos IZ. Cytotoxicity of denture base resins: effect of water bath and microwave postpolymerization heat treatments. *Int J Prosthodont*. 2004;17:340-4.
19. Campanha NH, Pavarina AC, Giampaolo ET, Machado AL, Carlos IZ, Vergani CE. Cytotoxicity of hard chairside relined resins: effect of microwave irradiation and water bath postpolymerization treatments. *Int J Prosthodont*. 2006;19:195-201.
20. International Standard ISO Specification 10993-1. Biological evaluation of medical devices. Part 1: Evaluation and testing within a risk management process. 3rd ed. Geneva, Switzerland: International Organization for Standardization; 2009.
21. International Standard ISO Specification 10993-5. Biological evaluation of medical devices. Part 5: Tests for in vitro cytotoxicity. 3rd ed. Geneva, Switzerland: International Organization for Standardization; 2009.
22. Arechabala B, Coiffard C, Rivalland P, Coiffard LJM, de Roek-Holtzhauer Y. Comparison of cytotoxicity of various surfactants tested on normal human fibroblast cultures using the neutral red test, MTT assay and LDH release. *J Appl Toxicol*. 1999;3:163-5.
23. Issa Y, Watts DC, Brunton PA, Waters CM, Duxbury AJ. Resin composite monomers alter MTT and LDH activity of human gingival fibroblasts in vitro. *Dent Mater*. 2004;20:12-20.
24. Neves CB [PhD thesis] Insights on the biodegradation of acrylic relined resins. Lisbon: University of Lisbon; 2012.
25. International Standard ISO Specification 7405. Dentistry – evaluation of biocompatibility of medical devices used in dentistry. 3rd ed. Geneva, Switzerland: International Organization for Standardization; 2008.
26. Chaves CA, Machado AL, Carlos IZ, Giampaolo ET, Pavarina AC, Vergani CE. Cytotoxicity of monomers, plasticizer and degradation by-products released from dental hard chairside relined resins. *Dent Mater*. 2010;26:1017-23.
27. Lai YL, Chen YT, Lee SY, Shieh TM, Hung SL. Cytotoxic effects of dental resin liquids on primary gingival fibroblasts and periodontal ligament cells in vitro. *J Oral Rehabil*. 2004;31:1165-72.
28. Feigal RJ, Yesilsoy C, Messer HH, Nelson J. Differential sensitivity of normal human pulp and transformed mouse fibroblasts to cytotoxic challenge. *Arch Oral Biol*. 1985;30:609-13.
29. Tsuchiya H, Hoshino Y, Tajima K, Takagi N. Leaching and cytotoxicity of formaldehyde and methylmethacrylate from acrylic resin denture base materials. *J Prosthet Dent*. 1994;71:618-24.
30. Lefebvre CA, Schuster GS, Marr JC, Knoernschild KL. The effect of pH on the cytotoxicity of eluates from denture base resins. *Int J Prosthodont*. 1995;8:122-8.
31. Schuster GS, Lefebvre CA, Dirksen TR, Knoernschild KL, Caughmann GB. Relationship between denture base resin cytotoxicity and cell lipid metabolism. *Int J Prosthodont*. 1995;8:580-6.
32. Cimpan MR, Cressey LI, Skaug N, Halstensen A, Lie SA, Gjertsen BT, et al. Patterns of cell death induced by eluates from denture base acrylic resins in U-937 human monoblastoid cells. *Eur J Oral Sci*. 2000;108:59-69.
33. Urban VM, Machado AL, Oliveira RV, Vergani CE, Pavarina AC, Cass QB. Residual monomer of relined acrylic resins. Effect of water-bath and microwave post-polymerization treatments. *Dent Mater*. 2007;23:363-8.
34. Urban VM, Machado AL, Vergani CE, Giampaolo ET, Pavarina AC, Almeida FG, et al. Effect of water-bath polymerization on the mechanical properties, degree of conversion, and leaching of residual compounds of hard chairside relined resins. *Dent Mater*. 2009;25:662-71.
35. Kedjarune U, Charoenworakul N, Koontongkaew S. Release of methyl methacrylate from heat-cured and autopolymerized resins: cytotoxicity testing related to residual monomer. *Aust Dent J*. 1999;44:25-30.
36. Neves CB, Lopes LP, Ferrão HF, Miranda JP, Castro MF, Bettencourt AF. Ethanol postpolymerization treatment for improving the biocompatibility of acrylic relined resins. *Biomed Res Int*. 2013, <http://dx.doi.org/10.1155/2013/485246>, 9 pp.
37. Koda T, Tsuchiya H, Yamauchi M, Hoshino Y, Takagi N, Kawano J. High performance liquid chromatographic estimation of eluates from denture base polymers. *J Dent*. 1989;17:84-9.
38. Koda T, Tsuchiya H, Yamauchi M, Ohtani S, Takagi N, Kawano J. Leachability of denture-base acrylic resins in artificial saliva. *Dent Mater*. 1990;6:13-6.
39. Vallittu PK, Ruyter IE, Buyukilimaz S. Effect of polymerization temperature and time on the residual monomer content of denture base polymers. *Eur J Oral Sci*. 1998;106:588-93.
40. Ruyter IE. Release of formaldehyde from denture base polymers. *Acta Odontol Scand*. 1980;38:17-27.
41. Baker S, Brooks SC, Walker DM. The release of residual monomeric methyl methacrylate from acrylic appliances in the human mouth: an assay for monomer in saliva. *J Dent Res*. 1988;67:1295-9.